

Viscoelastic effects and anomalous transient levelling exponents in thin films

M. BENZAQUEN¹, T. SALEZ¹ and E. RAPHAËL¹

¹ *Laboratoire de Physico-Chimie Théorique, UMR CNRS 7083 Gulliver - ESPCI ParisTech, 10 rue Vauquelin, 75005, Paris*

PACS 68.15.+e – Liquid thin films
PACS 83.60.Bc – Linear viscoelasticity
PACS 02.30.Jr – Partial differential equations

Abstract – We study theoretically the profile evolution of a thin viscoelastic film supported onto a no-slip flat substrate. Due to the nonconstant initial curvature at the free surface, there is a flow driven by Laplace pressure and mediated by viscoelasticity. In the framework of lubrication theory, we derive a thin film equation that contains local viscoelastic stress through the Maxwell model. Then, considering a small perturbation of the free surface, we linearise the equation and solve it by deriving its pseudo-Green’s function. We analyse and discuss in details the behaviour of this function. We then use it to study the viscoelastic evolution of a canonical Gaussian initial perturbation through its transient levelling exponent. For initial widths of the profile that are smaller than a characteristic length scale fixed by both the film thickness and the elastocapillary length, this quantity is shown to reach anomalously high values at the elastic-to-viscous transition. This prediction should in particular be observed at sufficiently short times in experiments on thin polymer films.

Over the past decades, the study of soft materials in confined geometries and thin films [1–3] has widely attracted the interest of physicists, biophysicists, chemists and engineers. In particular, thin polymer films are nowadays of major importance in several industrial applications such as biocompatible coatings, organic microelectronics and polymeric data storage devices. In order to gain insights into the behaviour of these films and their constitutive macromolecules, a wide class of experiments, including dewetting [4, 5], nanoindentation with gold particles [6], and levelling of stepped films [7–9], have been performed. Enhanced mobility effects in ultra-thin polymer films have been predicted [10, 11], and observed [12–14]. Film preparation by spincoating has also been widely studied [15–18], and is known to govern surface instabilities and pattern formation [19–21].

The evolution of the free surface of a thin Newtonian liquid film with nonconstant curvature is driven by the Laplace pressure and mediated by viscosity. This is well understood from the theoretical point of view through the so-called capillary-driven thin film equation [1–3, 22]. Although this equation remains only partially solved, several analytical [23–25] and numerical studies [26, 27] have been

performed and have allowed for a deeper understanding of its mathematical features. As for the diffusion equation [28], convergence of the solutions to intermediate asymptotic regimes [29] has been revealed. In particular, it was shown that the vertically-rescaled solution for any summable initial profile uniformly converges in time towards a universal self-similar attractor that is precisely given by the Green’s function of the capillary-driven linear thin film equation multiplied by the initial algebraic volume of the perturbation [30].

The aforementioned capillary-driven thin film equation describes the evolution of thin Newtonian films. Yet, thin films are often made of polymer melts which usually display viscoelastic properties [31, 32] in certain temporal ranges. In this case, some parts of the evolution may be different from that of a pure viscous fluid, as the deformation of the system in response to a given stress is now mediated by both elasticity and viscosity. The general understanding of viscoelasticity is of great interest in soft condensed matter and physics of glassy systems, as shown by the numerous recent results in the literature. New ways to probe the dynamics of viscoelastic materials have been explored [33]. Thin viscoelastic films have

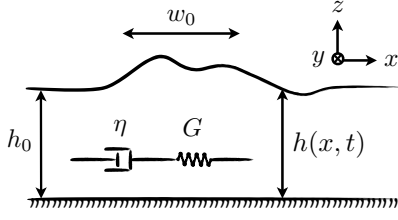


Fig. 1: Schematic of the vertical height profile $z = h(x, t)$, at horizontal position x and time t , of a thin viscoelastic film placed atop a flat substrate. The system is assumed to be spatially invariant in the other horizontal direction y . The typical horizontal length scale is denoted by w_0 , and the thickness at infinity by h_0 . The intern rheology of the viscoelastic fluid is accounted for through a local Maxwell model (see eq. (7)) of shear viscosity η and shear elastic modulus G , as symbolised by the cartoon showing the damper and spring in series.

been studied experimentally by dewetting [34, 35], and relaxation of nanoimprinted patterns [36, 37], in particular. From the theoretical point of view, viscoelastic thin film equations have been derived [3, 38–41], using the linear Jeffreys model.

In the present work, we recall the derivation of a viscoelastic thin film equation based on the Maxwell model, before linearising it and solving it analytically by deriving its pseudo-Green's function. In particular, we show that the regular part of this essential solution converges in time towards the Green's function of the purely viscous linear thin film equation [30]. Using these preliminary results, we then analyse the temporal relaxation of a canonical Gaussian height perturbation on a thin viscoelastic film, and study its evolution in terms of the transient levelling exponent [42]. Finally, we discuss the different observed regimes. We show in particular that the system displays anomalous – *i. e.* not comprised between the elastic and viscous standard values – transient levelling exponents for profile widths smaller than a characteristic length scale that is set by the film thickness and the elastocapillary length.

Viscoelastic thin film equation. – We consider a 2D thin viscoelastic film lying on a flat substrate (see Fig. 1). Let the origin O be taken at the substrate level, and let $z = h(x, t)$ be the vertical height profile of the film at horizontal position x and time t . The system is assumed to be spatially invariant in the other horizontal direction y . Let $\mathbf{u} = (u_x, u_z)$ be the 2D velocity field in the film. For an incompressible flow, the Navier-Stokes equation reads [43]:

$$\rho \frac{d\mathbf{u}}{dt} = -\nabla p + \nabla \sigma', \quad (1)$$

where ρ is the mass density of the material, p is the pressure, σ' is the extra-stress tensor [43], and $\frac{d}{dt} = \partial_t + \mathbf{u} \cdot \nabla$ is the convective derivative. Let h_0 be the thickness at infinity, w_0 be a typical horizontal dimension (see. Fig. 1), and

$\epsilon = h_0/w_0$. Within the the lubrication approximation, one has $\epsilon \ll 1$. We define the space and time dimensionless variables through $x = w_0 X$, $z = h_0 Z$, $h = h_0 H$, $t = t_0 T$, where t_0 is a typical time scale yet to be determined. Incompressibility implies that the dimensionless velocities read $u_x = v_0 U_X$ and $u_z = \epsilon v_0 U_Z$, where $v_0 = w_0/t_0$. In order to determine the scaling for pressure and time, we balance the typical gradients of Laplace pressure and viscous stress in eq. (1). This yields $p = (\gamma h_0/w_0^2)P = (\eta/(t_0 \epsilon^2))P$ which sets $t_0 = \eta w_0/(\gamma \epsilon^3)$, where γ is the surface tension and η is the viscosity. Finally, estimating the extra-stress tensor in the viscous limit, within the lubrication approximation, leads to:

$$\begin{pmatrix} \sigma'_{xx} & \sigma'_{xz} \\ \sigma'_{zx} & \sigma'_{zz} \end{pmatrix} = \frac{\eta}{t_0} \begin{pmatrix} \Sigma'_{XX} & \Sigma'_{XZ}/\epsilon \\ \Sigma'_{ZX}/\epsilon & \Sigma'_{ZZ} \end{pmatrix}. \quad (2)$$

Equation (1) then yields the following set of equations:

$$\epsilon^2 Re \frac{dU_X}{dT} = -\partial_X P + \epsilon^2 \partial_X \Sigma'_{XX} + \partial_Z \Sigma'_{XZ} \quad (3a)$$

$$\epsilon^4 Re \frac{dU_Z}{dT} = -\partial_Z P + \epsilon^2 \partial_X \Sigma'_{ZX} + \epsilon^2 \partial_Z \Sigma'_{ZZ}, \quad (3b)$$

where $Re = \rho v_0 w_0/\eta$ is the Reynolds number. In the framework of first order lubrication approximation in ϵ , eq. (3) simplifies to:

$$\partial_X P = \partial_Z \Sigma'_{XZ} \quad (4a)$$

$$\partial_Z P = 0. \quad (4b)$$

The boundary conditions at the free surface $Z = H(X, T)$ are set by the small-slope approximation of the Laplace pressure and the no-shear stress:

$$P|_{Z=H} \simeq -\partial_X^2 H \quad (5a)$$

$$\Sigma'_{XZ}|_{Z=H} = 0. \quad (5b)$$

Integrating eq. (4) together with eq. (5) leads to:

$$\Sigma'_{XZ} = (H - Z) \partial_X^3 H. \quad (6)$$

In order to account for the essence of shear viscoelasticity, we use the Maxwell model [31, 32]. This simple approach relates the local shear strain rate $\partial_t \epsilon_{xz} = \partial_z u_x$ and the local shear stress σ'_{xz} through:

$$\sigma'_{xz} + \tau \partial_t \sigma'_{xz} = \eta \partial_t \epsilon_{xz}, \quad (7)$$

where $\tau = \eta/G$ is the single characteristic time, with G being the shear elastic modulus. In dimensionless variables, eq. (7) reads:

$$\Sigma'_{XZ} + \mathcal{T} \partial_T \Sigma'_{XZ} = \partial_Z U_X, \quad (8)$$

where $\mathcal{T} = \tau/t_0$. Substituting eq. (6) into eq. (8) yields:

$$(1 + \mathcal{T} \partial_T) [(H - Z) \partial_X^3 H] = \partial_Z U_X, \quad (9)$$

and spatially integrating eq. (9) together with the no-slip boundary condition at the substrate, $U_X|_{Z=0} = 0$, leads to:

$$(1 + \mathcal{T}\partial_T) \left[\left(HZ - \frac{Z^2}{2} \right) \partial_X^3 H \right] = U_X. \quad (10)$$

In order to close the system we invoke mass conservation:

$$\partial_T H + \partial_X Q = 0, \quad (11)$$

where $Q = \int_0^H U_X dZ$. Combining eq. (10) and eq. (11), together with eq. (5a), yields at last:

$$\begin{aligned} \partial_T H = & -\partial_X \left[\frac{H^3}{3} \partial_X^3 H \right] \\ & -\mathcal{T} \partial_X \left[\frac{H^2}{2} \partial_T H \partial_X^3 H + \frac{H^3}{3} \partial_T \partial_X^3 H \right], \end{aligned} \quad (12)$$

that we will refer to as the viscoelastic thin film equation (VTFE). Note that by setting $\mathcal{T} = 0$ in eq. (12) one recovers the well know 2D capillary-driven thin film equation for Newtonian fluids [1–3, 22]. For the detailed derivation of a viscoelastic thin film equation using the Jeffreys model see [3, 39–41]. Equation (12) is a particular case of the latter for which the early time constant of the Jeffreys model has been set to zero.

Linearisation and pseudo-Green's function.

Let us now consider the case in which the surface perturbation is small compared to the overall thickness of the film. One can then write $H(X, T) = 1 + \zeta(X, T)$ where $|\zeta(X, T)| \ll 1$. In this limit, eq. (12) can be linearised as follows:

$$\partial_T \zeta = -\frac{1}{3} [\partial_X^4 \zeta + \mathcal{T} \partial_T \partial_X^4 \zeta]. \quad (13)$$

The factor 1/3 can be absorbed in time as $T \rightarrow 3T$ and $\mathcal{T} \rightarrow 3\mathcal{T}$ so that eq. (13) becomes:

$$\mathcal{L} \zeta(X, T) = 0, \quad (14)$$

where we introduced the linear differential operator:

$$\mathcal{L} = [\partial_T (1 + \mathcal{T} \partial_T^4) + \partial_X^4]. \quad (15)$$

Equation (14) is the linear viscoelastic thin film equation (LVTFE). The solution of Eq. (14), with the sufficiently regular initial condition $\zeta(X, 0) = \zeta_0(X)$, is given by the convolution of ζ_0 and the pseudo-Green's function $\mathcal{F}$ of the linear operator $\mathcal{L}$ where:

$$\mathcal{F}(X, T) = F(X, T) + e^{-T/\mathcal{T}} \delta(X), \quad (16)$$

and:

$$F(X, T) = \int \frac{dK}{2\pi} \left[\exp \left(-\frac{K^4 T}{1 + \mathcal{T} K^4} \right) - e^{-T/\mathcal{T}} \right] e^{iKX}. \quad (17)$$

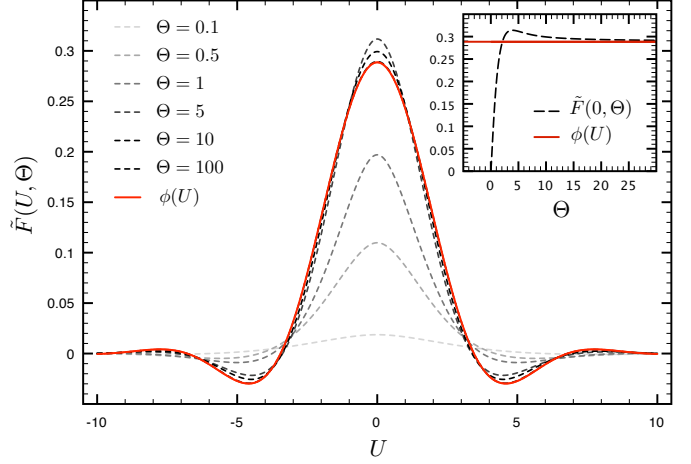


Fig. 2: Plot of the regular part $\tilde{F}(U, \Theta)$ of the normalised pseudo-Green's function of LVTFE as a function of U , as given by eqs. (16), (19), and (21), for different rescaled times Θ (dashed curves). The solid red line corresponds to $\phi(U)$ given that $\check{\mathcal{F}}_{\text{LTFE}}(U, T) = \phi(U)T^{-1/4}$ is the Green's function of the purely viscous linear thin film equation (LTFE), as defined in [30].

For clarity, we here refer to $\mathcal{F}$ as the pseudo-Green's function because it does not correspond to the solution $\mathcal{G}$ of the equation $\mathcal{L}\mathcal{G} = \delta$. Note also that the Jeffreys model would be likely to cancel the singular part of Eq. (16), as it includes a fluid-like behaviour at very short times. Based on the self-similar behaviours observed in previous studies [25, 30], we let the change of variables:

$$X = UT^{1/4} \quad (18a)$$

$$K = QT^{-1/4}, \quad (18b)$$

which, together with eq. (16), leads to:

$$T^{1/4} \check{\mathcal{F}}(U, T) = \tilde{F}(U, T) + e^{-T/\mathcal{T}} \delta(U), \quad (19)$$

where $\check{\mathcal{F}}(U, T) = \mathcal{F}(X, T)$ and:

$$\tilde{F}(U, T) = \int \frac{dQ}{2\pi} \left[\exp \left(-\frac{Q^4}{1 + \frac{\mathcal{T}}{T} Q^4} \right) - e^{-T/\mathcal{T}} \right] e^{iQU}. \quad (20)$$

Furthermore, defining the rescaled time $\Theta = T/\mathcal{T}$ we let $\tilde{F}(U, T) = \tilde{F}(U, \Theta)$ with:

$$\tilde{F}(U, \Theta) = \int \frac{dQ}{2\pi} \left[\exp \left(-\frac{Q^4}{1 + \Theta^{-1} Q^4} \right) - e^{-\Theta} \right] e^{iQU}. \quad (21)$$

Figure 2 shows a plot of the regular part $\tilde{F}(U, \Theta)$ of the normalised pseudo-Green's function of LVTFE as a function of U , as given by eqs. (16), (19), and (21), for different rescaled times Θ (dashed curves). The solid red line corresponds to $\phi(U)$, given that $\check{\mathcal{F}}_{\text{LTFE}}(U, T) = \phi(U)T^{-1/4}$ is the Green's function of the purely viscous linear thin film equation (LTFE), as defined in [30]. Note that in the

purely viscous case the pseudo-Green's function is equal to the Green's function. The inset shows the central value $\tilde{F}(0, \Theta)$ as a function of Θ . The function $\tilde{F}$ seems to converge in time to $\phi(U)$. This convergence can be proven rigorously. Indeed, for all $\Theta > 0$ and all Q one has:

$$\left| \left[\exp \left(-\frac{Q^4}{1 + \Theta^{-1} Q^4} \right) - e^{-\Theta} \right] e^{iQU} \right| \leq g(Q), \quad (22)$$

where $g(Q) = 2/(1 + Q^2)$ is a summable function. Therefore, invoking the dominated convergence theorem [46], one gets:

$$\begin{aligned} \lim_{\Theta \rightarrow +\infty} \tilde{F}(U, \Theta) &= \int \frac{dQ}{2\pi} e^{-Q^4} e^{iQU} \\ &= \phi(U). \end{aligned} \quad (23)$$

According to eqs. (19) and (21) one may thus write [30]:

$$\lim_{T \rightarrow +\infty} T^{1/4} \check{\mathcal{F}}(U, T) = T^{1/4} \check{\mathcal{F}}_{\text{LTFE}}(U, T). \quad (24)$$

Therefore, in the linear case, we recover the intuitive expectation that the longterm evolution of a thin viscoelastic film is well described by a purely viscous thin film equation. The corresponding convergence time sets the time window in which viscoelastic effects are important and need to be considered when studying the dynamics of the film. We expect this convergence time to scale like $\mathcal{T}$ and will study this in more details in the following through a canonical example.

Evolution of a Gaussian perturbation. — As mentioned in the previous section, the evolution of the surface displacement $\zeta(X, T)$ for a given initial condition $\zeta(X, 0) = \zeta_0(X)$ is given by the convolution of the pseudo-Green's function $\mathcal{F}(X, T)$ and $\zeta_0(X)$:

$$\begin{aligned} \zeta(X, T) &= (\mathcal{F} * \zeta_0)(X, T) \\ &= (F * \zeta_0)(X, T) + e^{-T/\mathcal{T}} \zeta_0(X), \end{aligned} \quad (25)$$

according to eqs. (16) and (17). Let us consider the case of a normalised Gaussian perturbation of the form:

$$\zeta_0(X) = \frac{1}{\sqrt{2\pi A^2}} e^{-X^2/(2A^2)}, \quad (26)$$

where $a = w_0 A$ is the initial horizontal width in real variables. In particular, we focus on the evolution of the central height $\zeta(0, T)$ of the perturbation for different values of the dimensionless initial width A . We let $\zeta(0, T) = \tilde{\zeta}(0, \Theta)$. Figure 3 shows a plot of $\log_{10} \tilde{\zeta}(0, \Theta)$ as a function of $\log_{10} \Theta$ as given by eq. (25) together with eq. (26), for different values of the rescaled dimensionless width $\hat{A} = A\mathcal{T}^{-1/4}$, but identical volume. As one can see, regardless of initial width, all the curves are attracted to the same $\Theta^{-1/4}$ grey dashed line at long times, that corresponds to the purely viscous evolution for the considered perturbation volume. Two different situations, that will be discussed in detail in the next part, can be identified in

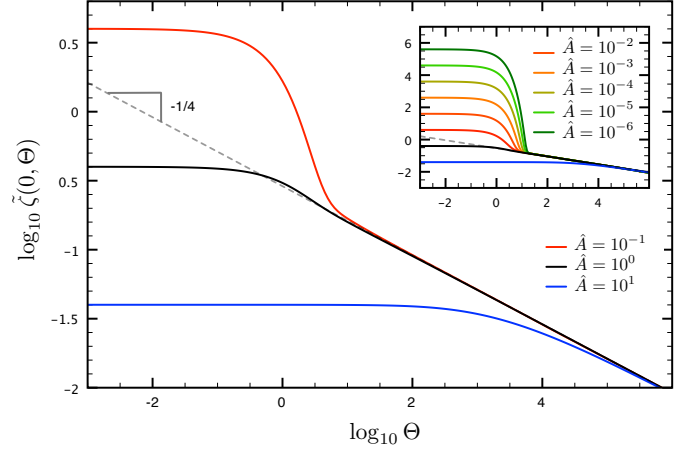


Fig. 3: Logarithmic amplitude $\log_{10} \tilde{\zeta}(0, \Theta)$ of the perturbation as a function of logarithmic rescaled time $\log_{10} \Theta$ as given by eqs. (25) and (26) for different values of the rescaled dimensionless initial width $\hat{A} = A\mathcal{T}^{-1/4}$, but identical volume. The inset shows the same plot for smaller values of $\hat{A}$. The grey dashed line corresponds to a purely viscous $\Theta^{-1/4}$ scaling.

regard to the existence or not of a change in concavity. For the case where concavity changes, the convergence occurs as expected at $\Theta \sim 1$, that is for $T \sim \mathcal{T}$. In this situation, the Maxwell time thus directly sets the timescale of the crossover between elastic and viscous behaviours.

Transient levelling exponent. — In a similar way to [42], we let the time-dependent levelling exponent $\alpha(\Theta)$ be defined as:

$$\tilde{\zeta}(0, \Theta) = \tilde{\zeta}(0, 0) \Theta^{-\alpha(\Theta)}. \quad (27)$$

or equivalently:

$$\alpha(\Theta) \doteq -\frac{\log_{10} \tilde{\zeta}(0, \Theta) - \log_{10} \tilde{\zeta}(0, 0)}{\log_{10} \Theta}. \quad (28)$$

The slopes of the curves in Fig. 3 read:

$$\frac{d \log_{10} \tilde{\zeta}(0, \Theta)}{d \log_{10} \Theta} = -\alpha(\Theta) - \alpha'(\Theta) \Theta \log_{10} \Theta, \quad (29)$$

which implies that for $\Theta = 0$, $\Theta = 1$, and $\Theta \rightarrow +\infty$ for which $\alpha'(\Theta) = 0$, the slopes of the curves correspond to the levelling exponent α . Note that this is also relevant for all time windows where $\alpha'(\Theta) \Theta \log_{10} \Theta \ll \alpha(\Theta)$, and thus in particular for the crossover region where $\Theta \sim 1$. Figure 4 shows a plot of the absolute values of the slopes of the curves in Fig. 3 as a function of reduced time Θ , for different rescaled widths $\hat{A}$ of the initial profile, but identical volume. In Figs. 3 and 4, two different situations can be distinguished. The first one is the situation for which the crossover from $\alpha = 0$ to $\alpha = 1/4$ happens with no change of concavity in Fig. 3 or, equivalently, with no overshoot in Fig. 4 (see blue curve with $\hat{A} = 10$ on both figures). The

second one is the situation for which the aforementioned crossover takes place with a change of concavity in Fig. 3 or, equivalently, with an overshoot in Fig. 4 (see curves $\hat{A} = 1$ and below on both figures). To understand the first situation, we recall that for a purely viscous liquid, a given initial perturbation takes a certain time T_{cv} to converge to the self-similar attractor [30, 44, 45]. In the particular linear case considered here, this time is expected to scale as the width of the initial perturbation to the power 4. Therefore, the first situation is that for which $T_{cv} \gg \mathcal{T}$ and the elastic delay of the evolution has no visible impact as it is shorter than that of the convergence towards the self-similar attractor. On the other hand, the second situation corresponds to $T_{cv} \ll \mathcal{T}$ and thus reveals the full viscoelastic behaviour. The transition between the two situations is thus given by $T_{cv} \sim \mathcal{T}$, which means $\hat{A}^4 = A^4 \mathcal{T}^{-1} \sim 1$, or in real variables:

$$a^4 \sim \tau \frac{\gamma h_0^3}{\eta} \sim \frac{\gamma h_0^3}{G}. \quad (30)$$

Note that one must also keep $h_0 \ll a$ for the lubrication approximation to remain valid. Interestingly, the transition between the two situations described above appears to be controlled by the ratio of the width of the perturbation to a new length scale that combines the elastocapillary length and the film thickness. This length scale is simply the length explored by levelling during a Maxwell time. We shall now focus on the second regime, namely $\hat{A} \ll 1$. To access this regime without breaking the lubrication hypothesis, one can think, for instance, of soft materials with small shear modulus G . Here, the clear overshoot in the slope (see Fig. 4) can give rise to what we will refer to as an anomalous transient levelling exponent. In fact, if an experimental system consisting of a thin viscoelastic film is explored within a time window that is in the vicinity of the maximum of the curve in Fig. 4, one may read a levelling exponent $\alpha > 1/4$. This value of the exponent is called *anomalous* since it is not comprised between the elastic (0) and viscous (1/4) standard values. Note that the temporal window of occurrence of this effect may be large due to the logarithmic scale of Fig. 4, and to the proportionality of real times with the time constant τ . In experimental systems where the viscoelastic timescale τ is large enough, as with glassy polymer films for instance, one therefore expects to observe an apparently constant and too large levelling exponent that may simply be the result of this anomalous viscoelastic transient overshoot. This result is somewhat analogous to the one highlighted previously by Christov and Stone for diffusion exponents in granular materials [42]. In their system, the origin of the anomalous scaling exponent is a non-constant diffusion coefficient that changes the structure of the diffusion equation and induces a loss of self-similarity.

Conclusion. — We have here presented a theoretical analysis of the capillary-driven relaxation of a thin viscoelastic film within the lubrication approximation. After

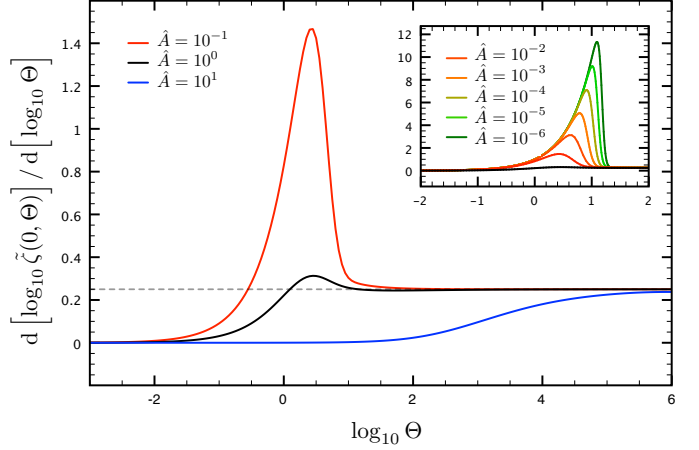


Fig. 4: Absolute values of the slopes of the curves in Fig. 3 as a function of reduced time Θ , for different rescaled dimensionless widths $\hat{A} = A\mathcal{T}^{-1/4}$ of the initial profile (see eq. (26)). The inset shows the same plot for smaller values of $\hat{A}$. The grey dashed line correspond to the purely viscous 1/4 exponent.

recalling the ingredients of the model, we derived a viscoelastic thin film equation that accounts for viscoelasticity through a Maxwell model. We linearised this equation and solved it by deriving its pseudo-Green's function. We proved that the pseudo-Green's function converges in time to that of the purely viscous linear thin film equation, which means that the longterm evolution of a thin viscoelastic film is well described by a purely viscous model. We then looked into the evolution of a canonical Gaussian initial perturbation and analysed it in terms of its transient levelling exponent. We discussed the different situations as a function of the initial width of the perturbation compared to a new length scale, that we identified and that combines the elastocapillary length and the film thickness. For small enough widths, provided that lubrication approximation remains valid, we revealed the possibility of observing anomalous transient levelling exponents if the system is explored within a certain time window around the characteristic viscoelastic time. We are confident that this work will be of interest for the study of the levelling dynamics of thin polymer films in the vicinity of the glass transition temperature, for which viscoelastic effects can be important.

* * *

The authors wish to thank A. Darmon, J. D. McGraw, K. Dalnoki-Veress and J. A. Forrest for interesting discussions.

REFERENCES

- [1] A. ORON, S. DAVIS, AND S. BANKOFF, *Rev. Mod. Phys.*, **69** (1997) 931.

- [2] R. V. CRASTER AND O. K. MATAR, *Rev. Mod. Phys.*, **81** (2009) 1131.
- [3] R. BLOSSEY, *Thin liquid films* (Springer, Dordrecht) 2012.
- [4] O. BÄUMCHEN, R. FETZER, AND K. JACOBS, *Phys. Rev. Lett.*, **103** (2009) 247801.
- [5] F. ZIEBERT AND E. RAPHAËL, *Phys. Rev. E*, **79** (2009) 031605.
- [6] Z. FAKHRAAI AND J. A. FORREST, *Science*, **319** (2008) 600.
- [7] J. D. MCGRAW, N. M. JAGO, AND K. DALNOKI-VERESS, *Soft Matter*, **7** (2011) 7832.
- [8] J. D. MCGRAW, T. SALEZ, O. BÄUMCHEN, E. RAPHAËL, AND K. DALNOKI-VERESS, *Phys. Rev. Lett.*, **109** (2012) 128303.
- [9] Y. CHAI, T. SALEZ, J. D. MCGRAW, M. BENZAQUEN, K. DALNOKI-VERESS, E. RAPHAËL, AND J. A. FORREST, *Science*, (2014) (in press).
- [10] F. BROCHARD WYART AND P.-G. DE GENNES, *Eur. Phys. J. E*, **1** (2000) 93.
- [11] L. SI, M. V. MASSA, K. DALNOKI-VERESS, H. R. BROWN, AND R. A. L. JONES, *Phys. Rev. Lett.*, **94** (2005) 127801.
- [12] R. L. JONES, S. K. KUMAR, D. L. HO, R. M. BRIBER, AND T. P. RUSSELL, *Nature*, **400** (1999) 146.
- [13] H. BODIGUEL AND C. FRETIGNY, *Phys. Rev. Lett.*, **97** (2006) 266105.
- [14] K. SHIN, S. OBUKHOV, J.-T. CHEN, J. HUH, Y. HWANG, S. MOK, P. DOBRIYAL, P. THIYAGARAJAN, AND T. P. RUSSELL, *Nature Materials*, **6** (2007) 961.
- [15] D. R. BARBERO AND U. STEINER, *Phys. Rev. Lett.*, **102** (2009) 248303.
- [16] L. E. STILLWAGON AND R. G. LARSON, *Physics of Fluids A: Fluid Dynamics*, **2** (1990) 1937.
- [17] G. REITER AND P.-G. DE GENNES, *Eur. Phys. J. E*, **6** (2001) 25.
- [18] A. RAEGER, M. CHOWDHURY, C. CALERS, A. SCHMATULLA, U. STEINER, AND G. REITER, *Phys. Rev. Lett.*, **105** (2010) 227801.
- [19] R. MUKHERJEE, A. SHARMA, AND U. STEINER, *Surface instability and pattern formation in thin polymer films, in generating micro- and nanopatterns on polymeric materials* (Wiley-VCH) 2011.
- [20] F. CLOSA, F. ZIEBERT, AND E. RAPHAËL, *Phys. Rev. E*, **83** (2011) 051603.
- [21] G. AMARANDEI, P. BELTRAME, I. CLANCY, C. O'DWYER, A. ARSHAK, U. STEINER, D. CORCORANA, AND U. THIELE, *Soft Matter*, **8** (2012) 6333.
- [22] S. E. ORCHARD, *Appl. sci. Res.*, **11** (1961) 451.
- [23] T. G. MYERS, *SIAM Rev.*, **40** (1998) 441.
- [24] M. BOWEN AND T. P. WITELSKI, *SIAM J. Appl. Math.*, **66** (2006) 1727.
- [25] T. SALEZ, J. D. MCGRAW, O. BÄUMCHEN, K. DALNOKI-VERESS, AND E. RAPHAËL, *Physics of Fluids*, **24** (2012) 102111.
- [26] A. BERTOZZI, *Notices of the AMS*, **45** (1998) 689.
- [27] T. SALEZ, J. D. MCGRAW, S. L. CORMIER, O. BUMCHEN, K. DALNOKI-VERESS, AND E. RAPHAËL, *Eur. Phys. J. E*, **35** (2012) 114.
- [28] J. FOURIER, *Théorie analytique de la chaleur* (Firmin Didot, père et fils) 1822.
- [29] G. I. BARENBLATT, *Scaling, self-similarity, and intermediate asymptotics* (Cambridge University Press) 1996.
- [30] M. BENZAQUEN, T. SALEZ, AND E. RAPHAËL, *Eur. Phys. J. E*, **36** (2013) 82.
- [31] C. W. MACOSKO, *Rheology principles, measurement and applications* (Wiley-VCH) 1994.
- [32] R. G. LARSON, *The structure and rheology of complex fluids* (OUP USA) 1999.
- [33] M. PELTON, D. CHAKRABORTY, AND E. MALACHOSKY, *Phys. Rev. Lett.*, **111** (2013) 244502.
- [34] S. HERMINGHAUS, K. JACOBS, AND R. SEEMANN, *Eur. Phys. J. E*, **12** (2003) 101.
- [35] H. BODIGUEL AND C. FRETIGNY, *Macromolecules*, **40** (2007) 7291.
- [36] Y. DING, H. W. RO, K. J. ALVINE, B. C. OKERBERG, J. ZHOU, J. F. DOUGLAS, A. KARIM, C. L. SOLES, *Advanced Functional Materials*, **18** (2008) 1854.
- [37] E. ROGNIN, S. LANDIS, AND L. DAVOUST, *Journal of Vacuum Science & Technology B: Microelectronics and Nanometer Structures*, **30** (2012) 011602.
- [38] R. KEUNINGS AND D. W. BOUSFIELD, *Journal of Non-Newtonian Fluid Mechanics*, **22** (219) 1987.
- [39] M. RAUSCHER, A. MÜNCH, B. WAGNER, AND R. BLOSSEY, *Eur. Phys. J. E*, **17** (2005) 373.
- [40] A. MÜNCH, B. WAGNER, M. RAUSCHER, AND R. BLOSSEY, *The European Physical Journal E*, **20** (2006) 365.
- [41] R. BLOSSEY, A. MÜNCH, M. RAUSCHER, AND B. WAGNER, *Eur. Phys. J. E*, **20** (2006) 267.
- [42] I. C. CHRISTOV AND H. A. STONE, *Proceedings of the National Academy of Sciences*, **109** (2012) 16012.
- [43] L. D. LANDAU AND E. M. LIFSHITZ, *Fluid Mechanics* (Pergamon Press) 1987.
- [44] O. BÄUMCHEN, M. BENZAQUEN, T. SALEZ, J. D. MCGRAW, M. BACKHOLM, P. FOWLER, E. RAPHAËL AND K. DALNOKI-VERESS, *Phys. Rev. E*, **88** (2013) 035001.
- [45] M. BACKHOLM, M. BENZAQUEN, T. SALEZ, E. RAPHAËL, AND K. DALNOKI-VERESS, *Soft Matter*, **88** (2014) DOI:10.1039/C3SM52940A.
- [46] RUDIN W., *Real and complex analysis* (McGraw-Hill Science) 1986.